

JPRS: 4306

MAIN FILE

4 January 1961

**PERMANENT FILE COPY**

**ELECTRICAL CONDUCTIVITY OF POLYMERS WITH  
CONJUGATED BONDS**

By Ye. I. Balabanov, et al.

- USSR -

**RETURN TO MAIN FILE**

DISTRIBUTION STATEMENT A  
Approved for public release;  
Distribution Unlimited

Distributed by:

OFFICE OF TECHNICAL SERVICES  
U. S. DEPARTMENT OF COMMERCE  
WASHINGTON 25, D. C.

19990503 083

U. S. JOINT PUBLICATIONS RESEARCH SERVICE  
1636 CONNECTICUT AVE., N.W.  
WASHINGTON 25, D. C.

ELECTRICAL CONDUCTIVITY OF POLYMERS WITH  
CONJUGATED BONDS

- USSR -


Following is a translation of the article by Ye. I. Balabanov, A. A. Berlin, V. P. Parini, V. L. Tal'roze, Ye. I. Frankevich, and M. I. Cherkashin entitled "Elektroprovodnost' polimerov s sopryazhennymi svyazyami" (English version above) in Doklady Akademii Nauk SSSR (Reports of the Academy of Sciences USSR), Vol 134, No 5, Moscow, 1960, pages 1123-1126.

(Presented by Academician V. N. Kondrat'yev  
14 June 1960)


In connection with the problem of obtaining organic polymeric substances with different electro-physical properties, including the problem of organic semiconductors, the extensive study (1) of electrical properties of different types of polymeric substances with systems of conjugated bonds and heterocyclic atoms in the conjugating chain is of interest. The authors have synthesized the class of polymers enumerated below and have made a study of their electrical conductivity and of its dependence on temperature.

1. Polymers with acyclic conjugating chains (2,3): polyphenylacetylene (1) and copolymers of polyphenylacetylene with hexyne (2) and with paradiethynylbenzene (3).


2. Polymers with benzene rings in the conjugating chain: polyphenylene

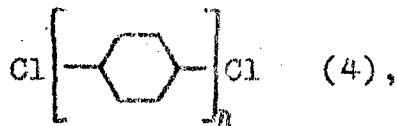



polyphenylenazo compounds (4-6) of the type

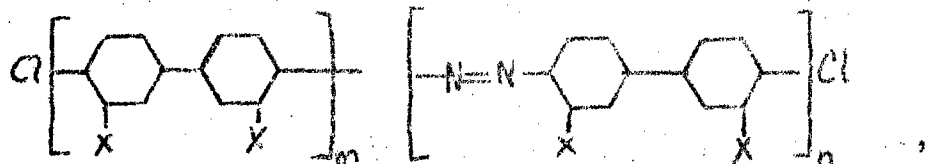


where X = H (5), CH<sub>3</sub> (6), COOH (7); polymeric aromatic and aliphatic-aromatic compounds containing quinoid and amino groups (7,8): polyphenylenaminoquinones of the type

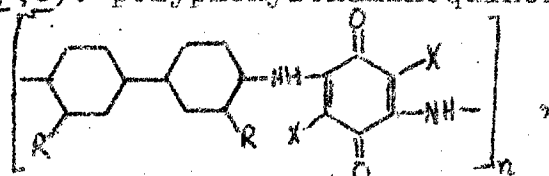



where X = H (8), Cl (9), with R = H and X = H (10) with R = COOH; poly-n-phenylenediaminoquinone (11), polyhexamethylenediaminoquinone (12)

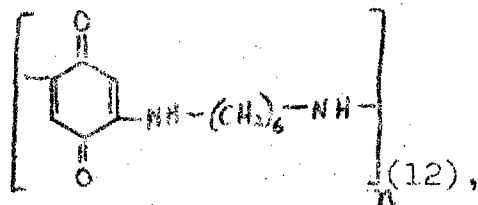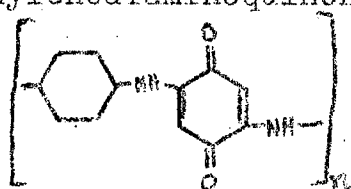


and polyphenylenazoquinones of the type

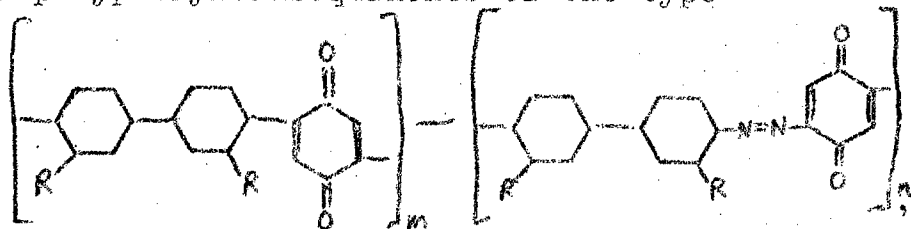

where R = H (13) and COOH (14); polymeric triazene (15), a substance containing quinonimino groupings (16)

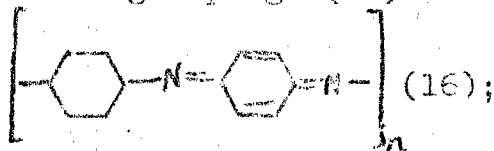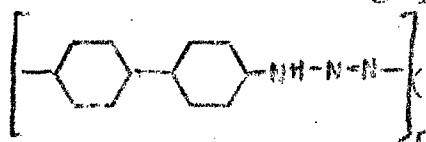


polymeric chelate compounds (9) of polydiphenylaminoquinone with metals (for example, copper) (17)

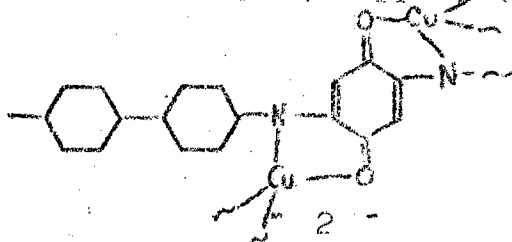

Molecular complexes of acenaphthene with chloranil (18) and with the pyridone derivative of polyphenylenaminoquinone (19) were also synthesized.

3. Compounds with nonbenzoid rings in the conjugating chains: tetrasalicylferrocene (20) and polymeric chelate complexes of it (10) with  $\text{Fe}^{++}$  and with  $\text{Be}^{++}$  (21,22)

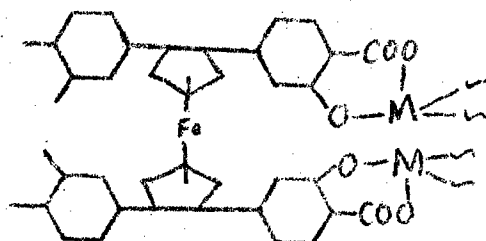

Polymeric chelate groups of percyanethylene with  $\text{Cu}^{++}$  (23) and with  $\text{Fe}^{++}$  (11,12).

The synthesis and properties of some of the above-enumerated compounds (for example, 8, 10, 11, 13, and 14) have up till now not been illuminated in publications. In the near future special publications will be devoted to them.

Polymers containing quinoid nuclei (10,14) in the conjugating chain, and particularly compounds in which the quinoid structure is connected to the chain by a hetero-atom of nitrogen (16), are of considerable interest. In such substances a sharp decrease in the energy excitation of the triplet state can be expected and, in some cases, also the formation of radical ionic structures.

The specimens investigated were, for the most part, tablets 10-12 mm in diameter.

In the present report we will limit ourselves to general characterization of the derived regularities. In all cases with temperature increase the electrical conductivity rose in accordance with the law,  $\sigma = \sigma_0 \cdot \exp(-E/kt)$  where  $\sigma_0$  and  $E$  are constants in the given example.

Deviations from this law occurred only close to the disintegration temperature level of the substance. The values of  $E$  obtained from 4.6 kilocal/mole (0.2 ev) for substance 16 to 49.5 kilocal/mole (2.1 ev) for polyphenylacetylene, and even up to 92 kilocal/mole for the complexes of acenaphthene with chloranil.

The manner of processing the specimens has a great effect on these parameters. Thus, for example, the size of the pre-exponent for polyphenylacetylene decreases 22 orders of magnitude in the transition from the film that was obtained from the solvent, to the tablet compressed

at 200° C.

There occurs, however, at this time a decrease in the "activation energy"  $E$ , so that the electrical conductivity of both specimens at room temperature appears to be approximately equal. A similar phenomenon in the sym-batic change of the pre-exponent and the activation ener-gy is often called a compensating effect, and there exist a series of analogies in chemical kinetics and catalysis, but for electrical conductivity observed on metal oxides (13). The nature of the compensating effect is still not clear; one of the theoretical approaches to the solution of the problem was examined recently (14).

It seemed that in our cases the compensating ef-fect appeared to be the rule covering all, or almost all, derived substances. This is especially graphically evi-dent from figure 1, where the given table 1 is broken down into coordinates  $\lg \sigma_0$  --  $E$ .

TABLE 1

| Spec.<br>Nr | $\sigma_0$ , $\text{ohm}^{-1}\text{cm}^{-1}$ | $E$ , $\frac{\text{kcal}}{\text{mole}}$ | $\sigma_{300^\circ\text{K}}$ | Remarks                                                           |
|-------------|----------------------------------------------|-----------------------------------------|------------------------------|-------------------------------------------------------------------|
| 1a          | $4 \cdot 10^{18}$                            | 49.5                                    | $10^{-17}$                   | Polymer film formed at 150° C                                     |
| 1b          | $5 \cdot 10^{17}$                            | 47.6                                    | $2 \cdot 10^{-17}$           | Polymerization conducted at 400° C                                |
| 1c          | $2 \cdot 10^{11}$                            | 37                                      | $3 \cdot 10^{-19}$           | Film from mixture of poly-mers 1a and 1b                          |
| 1d          | $3 \cdot 10^6$                               | 32.2                                    | $10^{-15}$                   | Fraction of specimen 1b dissolved in benzene                      |
| 1e          | $10^2$                                       | 22                                      | $10^{-14}$                   |                                                                   |
| 1f          | $2 \cdot 10^{-2}$                            | 8.5                                     | $10^{-3}$                    | Fraction of specimen 1b dissolved in pyridine                     |
| 1g          | $2 \cdot 10^{-4}$                            | 15.4                                    | $2 \cdot 10^{-15}$           | Polymerization conducted at 150° C, tablets com-pressed at 200° C |
| 2'          | $10^{10}$                                    | 49                                      | $10^{-15}$                   | Temperature range 20-50° C*                                       |
| 2''         | $5 \cdot 10^7$                               | 29                                      | ---                          | Temperature range 50-100° C                                       |
| 3           | $6.4 \cdot 10^{-6}$                          | 17.5                                    | $10^{-16}$                   | Specimen heated at 200° C                                         |
| 4           | $10^{-12}$                                   | 3.1                                     | $2 \cdot 10^{-16}$           |                                                                   |
| 5a          | 40                                           | 25                                      | $4 \cdot 10^{-17}$           | Without heating                                                   |
| 5b          | 1                                            | 21                                      | $10^{-15}$                   |                                                                   |
| 6           | 1-0.1                                        | 20-22                                   | $10^{-14}$ - $10^{-15}$      |                                                                   |
| 7           | 1                                            | 18.4                                    | $4 \cdot 10^{-14}$           |                                                                   |
| 8           | 30                                           | 24                                      | $10^{-16}$                   |                                                                   |
| 9           | $2 \cdot 10^3$                               | 23.7                                    | $10^{-15}$                   |                                                                   |

T A B L E 1 (continued)

| Spec. Nr. | $\sigma$<br>ohm <sup>-1</sup> .cm <sup>-1</sup> | E, kcal<br>mole | $\sigma$<br>300°K   | Remarks                                                            |
|-----------|-------------------------------------------------|-----------------|---------------------|--------------------------------------------------------------------|
| 10a       | 10 <sup>8</sup>                                 | 29              | 10 <sup>-13</sup>   | Derived under the same conditions                                  |
| 10b       | 10 <sup>-3</sup>                                | 9.2             | 2·10 <sup>-10</sup> |                                                                    |
| 11        | 10 <sup>-4</sup>                                | 20.2            | 2·10 <sup>-14</sup> | Derived under the same conditions                                  |
| 12        | 10 <sup>-7</sup>                                | 15.6            | 5·10 <sup>-16</sup> |                                                                    |
| 13a       | 10 <sup>-7</sup>                                | 13              | 2·10 <sup>-16</sup> |                                                                    |
| 13b       | 10 <sup>-8</sup>                                | 39              | 10 <sup>-20</sup>   |                                                                    |
| 14        | 5·10 <sup>4</sup>                               | 20.2            | 10 <sup>-10</sup>   | Temperature range 20-40°C                                          |
| 15a       | 50                                              | 23              | 10 <sup>-15</sup>   |                                                                    |
| 15b       | 6·10 <sup>6</sup>                               | 30.2            | 10 <sup>-15</sup>   |                                                                    |
| 16'       | 10 <sup>3</sup>                                 | 10.3            | 3·10 <sup>-9</sup>  |                                                                    |
| 16"       | 30 <sup>4</sup>                                 | 4.6             | ---                 | Temperature range 40-80°C                                          |
| 17        | 10 <sup>24</sup>                                | 25.4            | 4·10 <sup>-15</sup> | Ratio of acenaphthene:<br>chloranil 1:1; temperature range 20-50°C |
| 18a'      | 3·10 <sup>24</sup>                              | 67.5            | 3·10 <sup>-15</sup> |                                                                    |
| 18a"      | 5·10 <sup>25</sup>                              | 48.5            | ---                 | Temperature range 50-80°C                                          |
| 18b       | 6.4·10 <sup>41</sup>                            | 92              | 2·10 <sup>-15</sup> | Ratio of acenaphthene:<br>chloranil 1:2; temperature range 20-45°C |
| 19        | 3·10 <sup>4</sup>                               | 24.8            | 3·10 <sup>-3</sup>  | Substance 20a heated at 200°C                                      |
| 20a       | 10 <sup>-1</sup>                                | 12.6            | 10 <sup>-10</sup>   |                                                                    |
| 20b       | 5·10 <sup>-3</sup>                              | 12              | 10 <sup>-11</sup>   |                                                                    |
| 21        | 1                                               | 10.6            | 10 <sup>-5</sup>    |                                                                    |
| 22        | 5                                               | 11.7            | 10 <sup>-9</sup>    |                                                                    |
| 23        | 2                                               | 15.3            | 10 <sup>-11</sup>   |                                                                    |

\* Specimens whose straight line  $\lg \sigma \sim 1/T$  underwent fissure. Numbers with one and two strokes refer to the same specimen before and after fissure.

Some of the small numbers representing powers of ten appeared blurred in the original and so have not been typed with certainty.

Here we have an absolutely remarkable occurrence of the compensating effect in the range of sixty (1) orders of magnitude of change in the pre-exponent and a twenty-fold change in the activation energy for substances of different structure.

A series of specimens studied possesses electrical

conductivity surpassing the electrical conductivity of the common organic non-conductors by several orders of magnitude. This refers, first of all, to specimens 16, 21, and 22, which, in terms of their electrical conductivity, approach some of the organic semiconductors, known from publications (13-17).

- /Caption to Figure 1 on page 1125 of original, not reproduced here./:

Figure 1. Relation between the pre-exponent multiplier and the activation energy of electrical conductivity.

The strong dependence of  $\sigma$  to T, which is correlated with the high value of E, in cases of polyphenylacetylene (which are typical insulators at room temperature) is of great interest. In conjunction with a large  $\sigma$  this leads to the result that, with an increase in temperature the  $\sigma$  of polyphenylacetylene "attains" the  $\sigma$  of a whole series of polymers which show high electrical conductivity at room temperature.

One can expect that further investigations will permit us to establish the connection between electrophysical properties and the structure of single polymer molecules and the materials derived from them.

Institute of Chemical Physics  
Academy of Sciences USSR

Submitted  
11 June 1960

#### LITERATURE CITED

- 1) A. A. Berlin, V. P. Parini, Izvestiye vysshykh uchebnykh zavedeniy, seria khimii i khimicheskoi tekhnologii (News of the Higher Educational Institutions, Series on Chemistry and Chemical Technology), No 4, 122 (1958).
- 2) A. A. Berlin, M. I. Cherkashin, C. G. Sel'skaya, V. Ye. Limanov, Vysokomolekulniye soyedineniye (High-molecular-weight compounds), 1, No 12, 1817 (1959).
- 3) A. S. Berlin, L. A. Blyumenfel'd, M. I. Cherkashin, A. E. Kalmanson, C. G. Sel'skaya, Vysokomolekulniye soyedineniye, 1, No 9, 1362 (1959).
- 4) V. P. Parini, A. A. Berlin, Izv. AN SSSR, Ser. khim., No 12 (1958).
- 5) A. A. Berlin, V. P. Parini, Izv. AN SSSR, Ser. khim., No 9, 1674 (1959).
- 6) A. A. Berlin, V. I. Liogon'kiy, V. P. Parini, Vysokomolekulniye soed., 2, No 5, 689 (1960).
- 7) A. A. Berlin, N. G. Matveyeva, Vysokomolek. soed., 2, 1643 (1959).

# LITERATURE CITED (continued)

- 8) L. A. Blyumenfel'd, A. A. Berlin, N. G. Matveyeva, A. E. Kalmason, Vysokomolekurniye soed., 1, No 11, 1647 (1959).
- 9) A. A. Berlin, V. P. Parini, N. G. Matveyeva, Avt. svid. (Avtor svidetel'stvo -- Author's certificate), 128608 2 May 1959, classified page 39, 3.
- 10) A. A. Berlin, T. V. Kostroma, Avt. svid., 129018, 25 April 1959, classified page 39, 30.
- 11) A. A. Berlin, N. G. Matveyeva, A. I. Sherle, Izv. AN SSSR, Ser. khim., No 12, 2261 (1959).
- 12) A. A. Berlin, N. G. Matveyeva, A. I. Sherle, Avt. svid. 126612, 7 April 1959, classified page 39, 30.
- 13) W. Meyer, H. Neldel, Phys. Zs., 38, 1014 (1937).
- 14) S. Z. Poginskiy, Yu. L. Khant, DAN (Doklady Akademii Nauk), 130, No 2, 366 (1960).
- 15) A. V. Topchiyev, M. A. Geyderikh and others, DAN, 128, No 2, 312 (1959).
- 16) H. A. Pohl, Electronic News, 8-11-1960.
- 17) A. Epstein, B. S. Wildi, J. Chem. Phys., 32, 324 (1960).

10,123 -- Ed.  
10,065

-- END --